

METAL SOLUTIONS

EOS NickelAlloy IN939

Material Data Sheet

EOS NICKELALLOY IN939

Excellent High Temperature Performance with Corrosion Resistance

EOS NickelAlloy IN939 is a nickel-chromium alloy which provides an outstanding balance of high temperature strength, corrosion and oxidation resistance, fatigue performance and creep strength at temperatures up to 850 °C (1560 °F). Parts built from EOS NickelAlloy IN939 can be hardened after manufacture by application of precipitation-hardening heat treatments

MAIN CHARACTERISTICS

- Excellent mechanical properties
- Excellent corrosion and oxidation resistance
- High tensile, fatigue, creep and rupture strength at temperatures up to 850 °C (1 560 °F)
- Maintains good ductility in age-hardened condition
- Crack-free in as-built condition and resistant to strain-age cracking

TYPICAL APPLICATIONS

- Industrial gas turbines (vanes, blades, heat-shields)
- Microturbines
- Turbochargers
- Instrumentation parts
- Power industry parts
- Process industry parts


The EOS Quality Triangle

EOS uses an approach that is unique in the AM industry, taking each of the three central technical elements of the production process into account: the system, the material and the process. The data resulting from each combination is assigned a Technology Readiness Level (TRL) which makes the expected performance and production capability of the solution transparent.

EOS incorporates these TRLs into the following two categories:

- Premium products (TRL 7-9): offer highly validated data, proven capability and reproducible part properties.
- Core products (TRL 3 and 5): enable early customer access to newest technology still under development and are therefore less mature with less data.

All of the data stated in this material data sheet is produced according to EOS Quality Management System and international standards

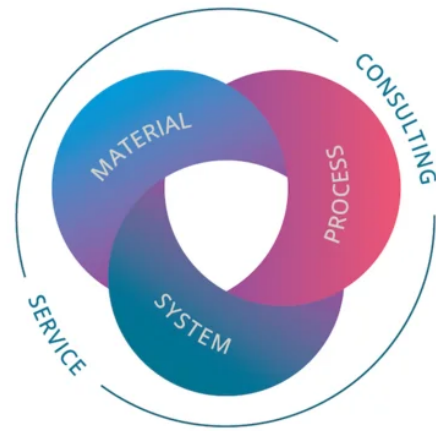


POWDER PROPERTIES

EOS NickelAlloy IN939 has the following chemical composition.

Powder Particle Size

GENERIC PARTICLE SIZE DISTRIBUTION

20 - 55 μm

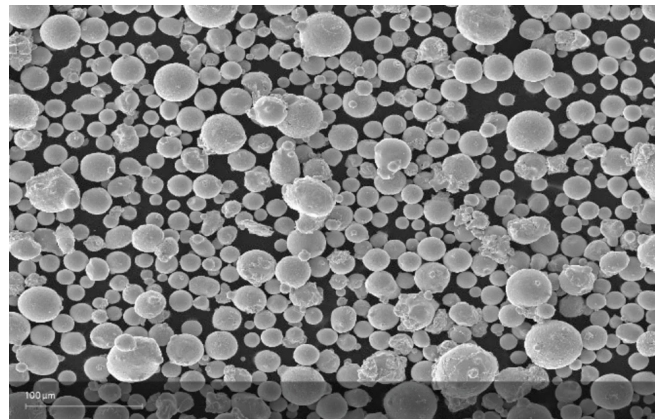

SEM micrograph of EOS NickelAlloy IN939 powder

HEAT TREATMENT

Description

The as-built microstructure of additively-manufactured IN939 consists of gamma phase (γ) and primary carbides. Heat treatment is required for the material to reach the desired microstructure and part properties through precipitation of the gamma prime (γ') strengthening phase. EOS has developed a short, AM-optimized 3-step heat treatment (14 hours at temperature), which results in similar or better properties than the commonly used 4-step heat treatment (50 hours at temperature). The gamma prime (γ') volume fraction after heat-treatment is in the range of 30 to 40 %.

Steps

Solution treatment:

Step 1: The purpose of this treatment is to homogenize the gamma matrix: Hold at 1190 °C for 4 hours followed by fast air / argon cooling.

Aging treatment: The purpose of aging steps is the precipitation and growth of gamma prime (γ') and carbides.

Step 2: Hold at 1000 °C for 6 hours, followed by fast air / argon cooling.

Step 3: Hold at 800 °C for 4 hours, followed by cooling in still air / argon.

HEADQUARTERS

EOS GmbH
Electro Optical Systems

Robert-Stirling-Ring 1
82152 Krailling / Munich
Germany

Tel.: +49 89 893 36-0
Email: info@eos.info
URL: www.eos.info

This powder has not been developed, tested or certified as a medical device according to Directive 93/42/EEC (MDD) or Regulation (EU) 2017/745 (MDR) and is not intended to be used as a medical device, in particular for the purposes specified in Art. 2 No. 1 MDR. Insofar as you intend to use the powder as raw material for the manufacture of pharmaceutical products or medical devices (e.g. as raw material which as a material must meet the requirements of Annex 1, Chapter II MDR), the responsibility and liability for all analyses, tests, evaluations, procedures, risk assessments, conformity assessments, approval and certification procedures as well as for all other official and regulatory measures required for this purpose shall lie solely with you both with regard to the pharmaceutical product and/or medical device manufactured by you and with regard to the properties, suitability, testing, evaluation, risk assessment, other requirements for use of the powder as raw material. In this respect, the limitations of liability pursuant to our General Terms and Conditions and the system sales or material contracts shall apply.

Part properties are provided for information purposes only and EOS makes no representation or warranty, and disclaims any liability, with respect to actual part properties achieved. Part properties are dependent on a variety of influencing factors and therefore, actual part properties achieved by the user may deviate from the information stated herein. This document does not on its own represent a sufficient basis for any part design, neither does it provide any agreement or guarantee about the specific properties of a material or part or the suitability of a material or a part for a specific application.

The achievement of certain part properties as well as the assessment of the suitability of this material for a specific purpose is the sole responsibility of the user. Any information given herein is subject to change without notice.

Status as of 18.05.2024. Subject to technical modifications. EOS is certified according to ISO 9001.

EOS®, Additive Minds® Alumide®, AMQ®, CarbonMide®, DirectMetal®, DMLS®, EOSAME®, EOSINT®, EOSIZE®, EOSPACE®, EOSPRINT®, EOSTATE®, EOSTYLE®, FORMIGA®, LaserProFusion®, PA 2200®, PrimeCast® and PrimePart® are registered trademarks of EOS GmbH Electro Optical Systems in some countries. For more information visit www.eos.info/trademarks.